

Synthesis and characterization of multiferroic $\text{BiMn}_7\text{O}_{12}$

F. Mezzadri,^{1,*} G. Calestani,^{1,2} M. Calicchio,² E. Gilioli,² F. Bolzoni,² R. Cabassi,² M. Marezio,³ and A. Migliori⁴

¹*Dipartimento di Chimica GIAF, Università di Parma, Viale G.P. Usberti 17A, I-43100 Parma, Italy*

²*Istituto dei Materiali per Elettronica e Magnetismo IMEM-CNR, Area delle Scienze, 43100 Parma, Italy*

³*CRETA CNRS, 38042 Grenoble Cedex 9, France*

⁴*CNR-IMM, Via Gobetti 101, I-40126 Bologna, Italy*

We report on the high pressure synthesis of $\text{BiMn}_7\text{O}_{12}$, a manganite displaying a "quadruple perovskite" structure. Structural characterization of single crystal samples shows a distorted and asymmetrical coordination around the Bi atom, due to presence of the $6s^2$ lone pair, resulting in non-centrosymmetric space group Im, leading to a permanent electrical dipole moment and ferroelectric properties. On the other hand, magnetic characterization reveals antiferromagnetic transitions, in agreement with the isostructural compounds, thus evidencing two intrinsic properties that make $\text{BiMn}_7\text{O}_{12}$ a promising multiferroic material.

PACS numbers: 61.05.cp, 61.05.jm, 75.30.-m, 75.47.Lx

Multiferroics are defined as materials that simultaneously exhibit more than one ferroic order parameter among ferromagnetism, ferroelectricity and ferroelasticity.¹ Although there are a lot of compounds presenting magnetic or ferroelectric order, the constraints required for their coexistence are so severe that only an extremely limited number of multiferroic materials exists. Besides scientific interest in their physical properties, multiferroics have potential for technological applications as actuators, switches, magnetic field sensors or new types of electronic memory devices. However, at present, only magnetoelectric composites, realized by combining magnetostrictive and piezoelectric materials, are ready for technological applications.² Typical multiferroics belong to the group of the perovskitic transition metal oxides, and include rare-earth manganites and ferrites (TbMnO_3 ,³ HoMn_2O_5 ,⁴ LuFe_2O_4 ⁵), bismuth-based compound BiFeO_3 ,⁶ non-oxides (BaNiF_4 ⁷) and spinel chalcogenides (ZnCr_2Se_4 ⁸). In usual perovskite-based materials, the ferroelectric distortion occurs due to the displacement of B-site cation (for example, Ti in BaTiO_3 ⁹) with respect to the oxygen octahedral coordination. One possible mechanism for the coexistence of ferroelectricity and magnetism, is the presence in the A-site of an atom carrying a non-bonding pair of electrons in an outer shell (lone-pair), whose stereochemical effect may be at the origin of ferroelectricity, while partially filled d orbitals on the B site should be responsible for the magnetic behavior. Examples include BiFeO_3 ⁶ and PbVO_3 .¹⁰ In these materials, the $6s^2$ lone-pair on the A-site cation (Bi^{3+} , Pb^{2+}) causes the Bi/Pb $6p$ (empty) orbital to come closer in energy to the O $2p$ orbitals. This leads to the hybridization between the Bi/Pb $6p$ and O $2p$ orbitals and drives the off-centering of the cation towards the neighboring anion resulting in ferroelectricity.

$\text{BiMn}_7\text{O}_{12}$ is a metastable material, belonging to the family of "quadruple-perovskite"^a manganites, with general formula $\text{AA}'_3\text{B}_4\text{O}_{12}$,^{11,12,13} derived by the doubling

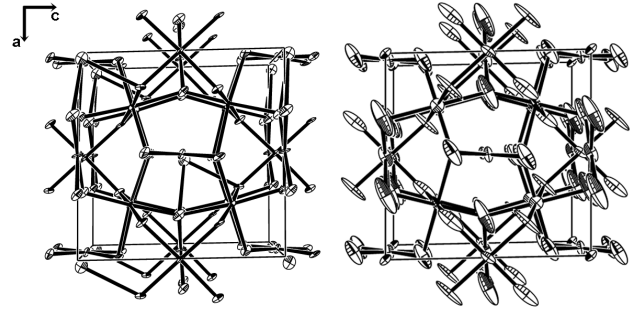


FIG. 1: ORTEP perspective view of the $\text{BiMn}_7\text{O}_{12}$ structure refined in Im (left) and $I2/m$ (right) space groups. Displacement ellipsoids are drawn in both cases at the 50% probability level.

of the conventional ABO_3 manganites axes. The complex and highly distorted structure is based on a 3D network of corner-sharing MnO_6 tilted octahedra, centred on the B site; it can only be accommodated under high pressure by the presence of a Jahn-Teller atom (Mn^{3+} or Cu^{2+}) on the A' site, displaying an uncommon square planar coordination due to large distortion of the standard dodecahedral coordination, typical of the A site. Since the occupation of the A site determines the properties of the compounds, the motivation of this work is the synthesis of the Bi-substitute member and to correlate the structural distortion induced by the Bi^{3+} lone pair to the electronic properties, in particular searching for multiferroic properties.

$\text{BiMn}_7\text{O}_{12}$ was synthesized by solid state reaction in high pressure/high temperature (HP/HT) conditions. Stoichiometric mixture of Mn_2O_3 (Ventron 98%) and Bi_2O_3 (Merck 99%) was used as reagent. They were mixed,

^a "quadruple" refers to the formula unit ABO_3

TABLE I: Atomic coordinates and parameters for BiMn₇O₁₂. U_{eq} is defined as one third of the trace of the orthogonalized U_{ij} tensor. Anisotropic displacement parameters: $U_{ij} = \exp(-2\pi^2(U_{11}h^2(a^*)^2 + \dots + 2U_{12}hk(a^*)(b^*) + \dots))$.

Atom	x	y	z	U_{eq}	U_{11}	U_{22}	U_{33}	U_{23}	U_{13}	U_{12}
Bi1	0.0284(6)	0	0.0173(6)	0.0255(3)	0.0247(8)	0.0307(3)	0.0210(5)	0	-0.0028(4)	0
Mn1	0.0030(30)	0	0.4951(3)	0.0106(6)	0.0066(15)	0.0185(10)	0.0066(16)	0	-0.0041(10)	0
Mn2	0.4997(4)	0	0.5019(4)	0.0102(6)	0.014(2)	0.0101(9)	0.0069(13)	0	-0.0041(11)	0
Mn3	0.4955(2)	0	-0.0022(4)	0.0101(6)	0.0034(14)	0.0082(9)	0.0185(14)	0	-0.0049(10)	0
Mn4	0.2542(3)	0.7419(3)	0.2540(3)	0.0083(4)	0.0080(10)	0.0076(6)	0.0093(8)	-0.0020(7)	-0.0031(7)	-0.0030(8)
Mn5	0.2476(2)	0.74930(17)	0.74590(18)	0.0067(5)	0.0066(12)	0.0084(6)	0.0049(10)	-0.0016(5)	-0.0046(7)	0.0006(6)
O1	0.3366(19)	$\frac{1}{2}$	0.1827(18)	0.015(2)	0.006(5)	0.023(5)	0.015(6)	0	-0.007(4)	0
O2	0.1916(19)	0	0.6755(19)	0.017(2)	0.010(6)	0.023(5)	0.017(6)	0	-0.007(4)	0
O3	0.1742(18)	0	0.3031(18)	0.017(2)	0.004(5)	0.029(6)	0.017(6)	0	-0.001(4)	0
O4	0.825(2)	0	0.3094(19)	0.020(3)	0.012(6)	0.029(6)	0.017(6)	0	-0.010(5)	0
O5	0.4910(16)	0.8086(13)	0.3282(14)	0.0196(19)	0.016(4)	0.028(4)	0.015(4)	-0.015(3)	-0.006(3)	-0.006(4)
O6	0.3081(15)	0.8259(10)	-0.0105(14)	0.0192(15)	0.019(4)	0.016(4)	0.023(4)	0.001(3)	-0.009(3)	-0.001(3)
O7	0.0167(14)	0.6830(13)	0.1765(15)	0.0197(19)	0.009(4)	0.031(4)	0.019(4)	-0.010(3)	-0.006(3)	-0.010(4)
O8	0.6796(15)	0.1800(10)	0.0112(13)	0.0162(15)	0.017(4)	0.015(4)	0.016(4)	0.000(3)	-0.008(3)	-0.002(3)

TABLE II: Interatomic distances (Å).

Atoms	Distance	Atoms	Distance
Bi1-O3	2.392(14)	Mn3-O6	2x1.910(10)
Bi1-O6	2x2.481(9)	Mn3-O8	2x1.923(10)
Bi1-O7	2x2.631(10)		
Bi1-O5	2x2.697(10)	Mn4-O7	1.920(12)
Bi1-O4	2.706(13)	Mn4-O5	1.922(13)
Bi1-O2	2.872(15)	Mn4-O1	1.969(6)
Bi1-O1	2.874(14)	Mn4-O3	2.035(5)
Bi1-O8	2x2.945(11)	Mn4-O8	2.076(11)
		Mn4-O6	2.130(11)
Mn1-O1	1.907(14)		
Mn1-O4	1.916(16)	Mn5-O8	1.897(10)
Mn1-O2	1.943(16)	Mn5-O6	1.961(11)
Mn1-O3	1.956(13)	Mn5-O2	1.969(6)
		Mn5-O4	1.986(6)
Mn2-O7	2x1.887(11)	Mn5-O5	2.087(12)
Mn2-O5	2x1.925(10)	Mn5-O7	2.163(11)

finely grounded in glove box and encapsulated in a Pt foil inserted in the MgO octahedral cell and in the multi anvil apparatus. The pressure was increased up to its maximum value at a rate of 160 bar/min, then the capsule was heated up to the reaction temperature at a rate of 50°C/min. The optimal conditions for the synthesis of a mixture of bulk material and single crystals were identified as 40 Kbar and 1000°C. After 2 hours in these conditions the sample was cooled down to room temperature by switching off the heater. The pressure was finally slowly released at 0.4 bar/min.

The crystal structure of BiMn₇O₁₂ at RT was determined by single crystal X-ray diffraction. Intensity data were collected by using MoK α data in the range $3.79 \leq \theta \leq 28.83^\circ$ on a Bruker AXS Smart diffractometer, equipped with a CCD area-detector. The structure is monoclinic, with lattice parameters $a = 7.5351(15)$, $b = 7.3840(15)$, $c = 7.5178(15)$ Å and $\beta = 91.225(3)^\circ$. The cell volume is $V = 418.19(15)$ Å³, consistent with 2

formula units per cell. In analogy with other monoclinic AMn₇O₁₂ compounds, the structure was initially refined with SHELX97¹⁴ in the centrosymmetric space group I2/m, using anisotropic atomic displacements parameters (a.d.p.'s) for all the atoms. The refinement converged to $R_1 = 0.0535$, $wR_2 = 0.1413$ and g.o.f = 1.101 for 562 data and 59 parameters. In spite of the fact that these final agreement indices can be considered satisfactory, when the sole numeric values are considered, a careful inspection of the refined parameters points out a very unusual trend of the a.d.p.'s showing, in particular for the oxygen atoms, not only very high values but also an anomalous elongation in a common direction of the ac plane (Fig.1), that indicates static disorder. Therefore the possibility of an artifact induced by forcing an acentric structure in a centric symmetry was taken into account and the structure was further refined in the noncentrosymmetric I2 and Im space groups. While the results obtained in I2 are comparable to those of the centrosymmetric model, the ones produced in Im are characterized by a significant improvement in terms of agreement indices ($R_1 = 0.0391$, $wR_2 = 0.0928$ and g.o.f = 1.113 for 1082 data and 103 parameters) and a.d.p.'s. The latter is clearly evidenced in Fig.1, that shows a comparison of the ORTEP¹⁵ plots of the crystal structure of BiMn₇O₁₂ refined in both Im and I2/m, in which the a.d.p.'s are represented by ellipsoids drawn at the 50% probability level. Atomic parameters, refined in the acentric space group Im, and relevant bond distances are shown in Table I and II, respectively. Charge distribution analysis, performed with CHARDIS,¹⁶ indicates a 3+ oxidation state for all the Mn atoms. The decrease of symmetry from the centrosymmetric space group I2/m, typical of other monoclinic A³⁺Mn₇O₁₂ compounds, to Im in BiMn₇O₁₂ is mainly determined by the steric hindrance of the 6s² lone pair of the Bi³⁺ ion. This typically produces a quite distorted coordination around the Bi atom, with the strongest bonds lying on the same side in order

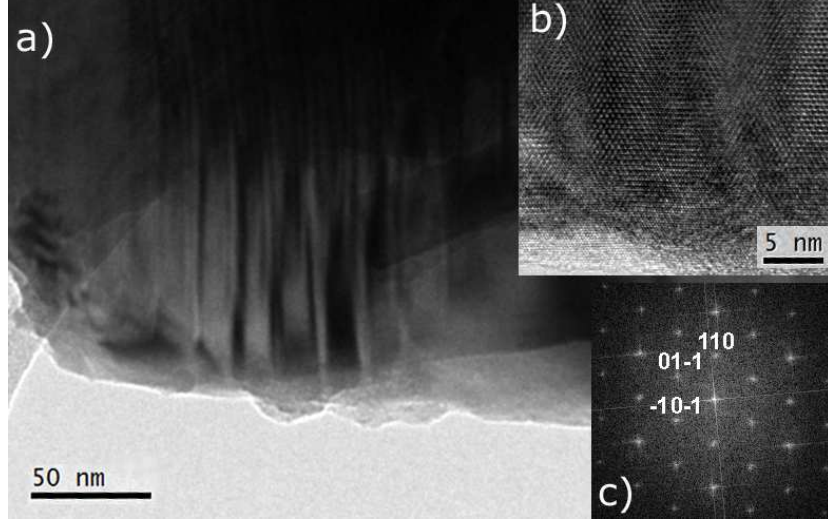


FIG. 2: Bright Field (a) and High Resolution (b) TEM images taken in the $[-111]$ zone axis showing the presence of twinning domains in a $\text{BiMn}_7\text{O}_{12}$ sample. Fast fourier transform of the HREM image is shown in (c).

to accommodate the lone pair on the opposite one. Structural data suggest that the Bi atom moves out from the center of the icosahedral oxygen coordination determining an asymmetrical coordination. An electrical polarization of $7.33 \mu\text{C}/\text{cm}^2$ at RT, generated by the displacement of all the Bi atoms in a common direction, can be computed by a simple model as dipole moment for volume unit, suggesting the existence of ferroelectricity in $\text{BiMn}_7\text{O}_{12}$. A similar value was reported⁶ for the simple perovskite BiFeO_3 , where a spontaneous polarization of $6.1 \mu\text{C}/\text{cm}^2$ was measured at 77 K on bulk samples. This hypothesis is further supported by TEM investigations, performed on a Philips TECNAI F20 transmission electron microscope operating at 200 KV, which show the presence of twinning domains extending on a few tens of nanometers, evidenced in Fig.2a and Fig.2b by sharp contrast variations. The domains orientation is consistent with the inversion of the polar axis, namely the shift of the Bi ions in opposite directions.

The magnetic properties of $\text{BiMn}_7\text{O}_{12}$ have been studied using a SQUID magnetometer. The measurements were carried out on polycrystalline samples because the single crystals yielded a too weak signal, approaching the instrumental sensitivity. The Zero Field Cooled (ZFC) and Field Cooled (FC) DC magnetization curves in applied magnetic field $H = 10$ Oe are reported in Fig.3 (upper panel), where a sharp transition to antiferromagnetic regime at $T_c \approx 50$ K can be seen. The antiferromagnetic nature of the ordered phase is more clear looking at the inverse susceptibility shown in Fig.3 (lower panel), where one can also estimate the Curie-Weiss temperature $\theta \approx 206$ K. The anomaly at T

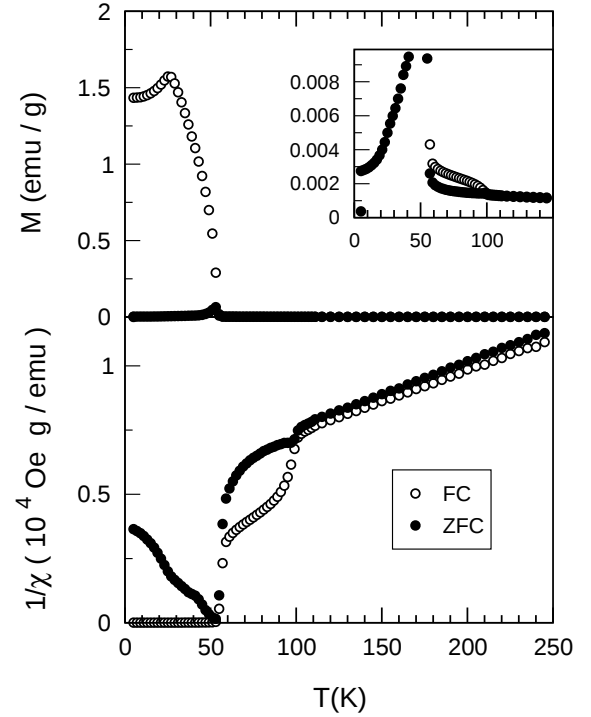


FIG. 3: Zero Field Cooled (ZFC, filled symbols) and Field Cooled (FC, open symbols) DC magnetization curves (upper panel) and inverse susceptibility (lower panel) in applied magnetic field $H = 10$ Oe. Inset: secondary transition in the magnetization curve at $T \approx 100$ K.

≈ 100 K could be ascribed to the possible presence of BiMnO₃ impurities, whose monoclinic phase undergoes a ferromagnetic transition at $T_c = 99$ K¹⁷ recoverable in an amplified view of the magnetization curve (inset of Fig.3). From the magnetization of BiMnO₃¹⁸ one can assess that the impurity would be less than 1%. The sharp drop of the inverse susceptibility at T_c has the shape usually observed in stoichiometrically pure Dzyaloshinskii-Moriya compounds,^{19,20} which is consistent with the MnO₆ octahedra tilting. It is worth to remark that a similar behavior is also observed in the structurally related compounds PrMn₇O₁₂²¹ and LaMn₇O₁₂,¹² while is absent in the simple perovskite BiMnO₃. A detailed study of the magnetic structure by neutron diffraction is in progress. The slope of the inverse susceptibility yields $\approx 6 \mu_B/\text{Mn}$, while the expected value for Mn³⁺ ions would be $4.9 \mu_B/\text{Mn}$. The antiferromagnetic peak at 26 K should correspond to the ordering of the Mn ions in the planarly coordinated A' sites.

In conclusion, we have synthesized by HP/HT BiMn₇O₁₂, a new member of the intriguing family of manganites with quadruple perovskite structure.

Detailed structural characterization carried out by single crystal X-ray diffraction yields the definition of a non-centrosymmetric space group (Im) never observed before in this class of compounds. This feature is originated by the stereochemical effect induced by the presence of the 6s² lone pair of the Bi³⁺ ions, that induces an asymmetrical coordination of the oxygen neighbors, leading to a permanent electrical dipole moment. Magnetic characterization points out, in agreement with isostructural compounds, the presence of antiferromagnetic transitions at 50 and 26 K should correspond to the ordering of the B and A' sites respectively. The coexistence of the two ferroic orders makes of BiMn₇O₁₂ a new promising multiferroic material.

The authors wish to express their gratitude to G. André, F. Bourée, A. Gauzzi, G. Rousse, A. Prodi, F. Licci for fruitful discussions and to T. Besagni for XRD. A few high pressure experiments of BiMn₇O₁₂, were performed at the Bayerisches Geoinstitut at Bayreuth (Germany) under the EU "Research Infrastructures: Transnational Access" Programme (Contract No.505320 (RITA)- High Pressure).

-
- | * | Corresponding | Author. | E-mail: |
|---------------|--|---------|----------------------------------|
| | | | francesco.mezzadri@nemo.unipr.it |
| ¹ | H. Schmid, <i>Ferroelectrics</i> 162 , 317 (1994). | | |
| ² | Ce-Wen Nan, M.I. Bichurin, Shuxiang Dong, D. Viehland, and G. Srinivasan, <i>J. Appl. Phys.</i> 103 , 031101 (2008). | | |
| ³ | T. Kimura, T. Goto, H. Shintani, K. Ishizaka, T. Arima, and Y. Tokura, <i>Nature</i> 426 , 55 (2003). | | |
| ⁴ | G.R. Blake, L.C. Chapon, P.G. Radaelli, S. Park, N. Hur, S-W. Cheong, and J. Rodríguez-Carvajal, <i>Phys. Rev. B</i> 71 , 214402 (2005). | | |
| ⁵ | N. Ikeda, H. Ohsumi, K. Ohwada, K. Ishii, T. Inami, K. Kakurai, Y. Murakami, K. Yoshii, S. Mori, Y. Horibe, and H. Kitô, <i>Nature</i> 436 , 1136 (2005). | | |
| ⁶ | J. Wang, J.B. Neaton, H. Zheng, V. Nagarajan, S.B. Ogale, B. Liu, D. Viehland, V. Vaithyanathan, D.G. Schlom, U.V. Waghmare, N.A. Spaldin, K.M. Rabe, M. Wuttig, and R. Ramesh, <i>Science</i> 299 , 1719 (2003). | | |
| ⁷ | C. Ederer and N.A. Spaldin, <i>Phys. Rev. B</i> 74 , 024102 (2006). | | |
| ⁸ | T. Rudolf, Ch. Kant, F. Mayr, J. Hemberger, V. Tsurkan, and A. Loidl, <i>Phys. Rev. B</i> 75 , 052410 (2007). | | |
| ⁹ | H.D. Megaw, <i>Acta Cryst.</i> 5 , 739 (1952). | | |
| ¹⁰ | D.J. Singh, <i>Phys. Rev. B</i> 73 , 094102 (2006). | | |
| ¹¹ | A. Prodi, E. Gilioli, A. Gauzzi, F. Licci, M. Marezio, F. Bolzoni, Q. Huang, A. Santoro, and J.W. Lynn, <i>Nature Materials</i> 3 , 48 (2004). | | |
| ¹² | A. Prodi, F. Licci, R. Cabassi, F. Bolzoni, E. Gilioli, Q. Huang, A. Santoro, J.W. Lynn, M. Affronte, A. Gauzzi and M. Marezio, to be published. | | |
| ¹³ | B. Bochu, J. Chenavas, C. Joubert, and M. Marezio, <i>J. of Solid State Chemistry</i> 11 , 88 (1974). | | |
| ¹⁴ | G.M. Sheldrick, SHELX97, Program for crystal structure refinement, University of Goettingen, Germany (1997). | | |
| ¹⁵ | Michael N. Burnett and Carroll K. Johnson, ORTEP-III: Oak Ridge Thermal Ellipsoid Plot Program for Crystal Structure Illustrations, Oak Ridge National Laboratory Report ORNL-6895 (1996). | | |
| ¹⁶ | M. Nespolo, G. Ferraris, and H. Ohashi, <i>Acta Cryst. B</i> 55 , 902 (1999). | | |
| ¹⁷ | E. Montanari, G. Calestani, A. Migliori, M. Dapiaggi, F. Bolzoni, R. Cabassi, and E. Gilioli, <i>Chem. Mater.</i> 17 , 6457 (2005). | | |
| ¹⁸ | E. Montanari, G. Calestani, L. Righi, E. Gilioli, F. Bolzoni, K.S. Knight, and P.G. Radaelli, <i>Phys. Rev. B</i> 75 , 220101(R) (2007). | | |
| ¹⁹ | J. Topfer and J.B. Goodenough, <i>J. Solid State Chem.</i> 130 , 117 (1997). | | |
| ²⁰ | J. Hemberger, F. Schrettle, A. Pimenov, P. Lurkenheimer, V. Yu. Ivanov, A.A. Mukhin, A.M. Balbashov, and A. Loidl, <i>Phys. Rev. B</i> 75 , 035118 (2007). | | |
| ²¹ | F. Mezzadri, M. Calicchio, E. Gilioli, R. Cabassi, F. Bolzoni, G. Calestani, and F. Bissoli, <i>Phys. Rev. B</i> , Submitted. | | |